

Characteristic features of d pairing in bilayer cuprates under conditions of Peierls instability of the normal phase

M. V. Eremin* and I. A. Larionov

Physics Department, Kazan State University, 420008 Kazan, Russia

Abstract

A system of self-consistent integral equations for the superconducting gap is formulated and solved taking account of the instability of the normal phase of bilayered cuprates against charge-density waves. The critical parameters are calculated as a function of the wave vector, temperature, and doping index. It is found that the region in which superconductivity coexists with d-type charge-density waves depends strongly on the doping index. The effective energy-gap parameter, determined as the interval between the peaks of the density of states, can have a local minimum at temperatures $T < T_C$.

Journal ref:

Pis'ma Zh. Eksp. Teor. Fiz. 68, No. 7, 583-587, (1998)

JETP Lett. vol. 68, # 7, pp. 611-615, 10 October 1998

* corresponding author, e-mail: Mikhail.Eremin@ksu.ru

PACS numbers: 74.72.-h, 74.25.Jb

Typeset using REVTeX

It can now be regarded as an established experimental fact that d-type pairing is realized in most layered cuprates, and in addition the determining component of the order parameter of the pseudogap in the normal phase of underdoped samples possesses the same d-type symmetry.^{1,2} At least this conclusion does not raise any objections for $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$, $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8-\delta}$, and other bilayer cuprates. The question of the nature of the pairing and the origin of the pseudogap in the normal phase is still open. Specifically, it is still not clear whether or not they are interrelated or completely independent. In the present letter we show that the empirical dependences of T_C and the pseudogap closure temperature T^* on the doping index and the dependences of their order parameters on the wave vector can be qualitatively understood in a model of a quasi-two-dimensional metal with strong electronic correlations, in which case the gap in the elementary excitations spectrum is due to anomalous averages of the type $\langle \Psi_{\mathbf{k}}^{2\sigma} \Psi_{\mathbf{k}+\mathbf{q}}^{2\sigma} \rangle$, characteristic for a Peierls instability of the normal phase. The problem of the existence of superconductivity under conditions of Peierls instability is a classic problem. For ordinary metals it has been discussed in a number of works (see, for example, Refs. 3 and 4), where the anomalous averages were due to the Fröhlich interaction and did not depend on the wave vector. In the present letter the main interaction responsible for the formation of the superconducting state is the short-range superexchange interaction, and the normal phase exhibits strongly non-Fermi-liquid behavior. The spectral weight of the conduction band under study depends nonlinearly on the doping index, and it is already half-filled when the number of holes per unit cell of the Cu_2O_4 bilayer is $2/7$ (Ref. 5) instead of 1, as would have happened in the case of normal metals.

To describe the subsystem of current carriers in bilayer high- T_C superconductors we employ a Hamiltonian of the form

$$\hat{H} = \sum_{l\sigma} \varepsilon_p \Psi_l^{\sigma,\sigma} + \sum_{lm} t_{lm}^{pp} \Psi_l^{2,\sigma} \Psi_m^{\sigma,2} + \sum_{l>m} j_{lm} \left[2 (\bar{S}_l \bar{S}_m) - \frac{n_l n_m}{2} \right] + \sum_{l>m} g_{lm} \delta_l \delta_m, \quad (1)$$

where $\Psi_m^{2\sigma} (\Psi_m^{\sigma 2})$, are Hubbard-type operators corresponding to creation (annihilation) of quasiparticles in the bonding singlet-correlated oxygen band,⁶ $n_l = \Psi_l^{\uparrow\uparrow} + \Psi_l^{\downarrow\downarrow}$, $\delta_l = n_l + 2\Psi_l^{22}$, and, j_{lm} and g_{lm} are the superexchange and Coulomb interactions parameters. The

quasiparticle dispersion relation has the form

$$\varepsilon_{\mathbf{k}} = P_{pd}[2t_1(\cos \mathbf{k}_x a + \cos \mathbf{k}_y a) + 4t_2 \cos \mathbf{k}_x a \cos \mathbf{k}_y a + 2t_3(\cos 2\mathbf{k}_x a + \cos 2\mathbf{k}_y a)] - \mu, \quad (2)$$

where μ is the chemical potential, which under optimal doping, according to photoemission data,⁷ lies 10 meV below the saddle peak of the density of states, $P_{pd} = (2 + \delta)/4$ is the average value of the anticommutators $\{\Psi_m^{2\sigma}, \Psi_m^{\sigma 2}\}$ with tunneling taken into account, δ is the number of current carriers per unit cell in the Cu_2O_4 bilayer, a is the lattice constant, and $t_1 = t_1^{(0)}[1 + \langle S_i S_j \rangle / P_{pd}^2]$. We take the following parameter set, which is consistent with the Fermi surface and the temperature behavior of the spin susceptibility of the normal phase of $\text{YBa}_2\text{Cu}_4\text{O}_8$: $t_1^{(0)} = 70$ meV, $t_2^{(0)} = 0$, and $t_3^{(0)} = 5$ meV.⁸ Following Ref. 9, we give the spin correlation functions of the nearest neighbors phenomenologically as $\langle S_i S_j \rangle = (-0.2 \exp(0.6 + \delta/2)^{-1} + 0.6)/1.8356$, so that the width of the band would approach zero as $\delta \rightarrow 0$, which is necessary for a correct description of the insulator-metal transition in these compounds.

In the mean-field approximation the elementary excitations spectrum of the Hamiltonian (1) is determined by the equation

$$\det \begin{vmatrix} \varepsilon_{\mathbf{k}} - E & G_{\mathbf{k}+\mathbf{Q}} & \Delta_{\mathbf{k}} & U_{\mathbf{k}} \\ G_{\mathbf{k}} & \varepsilon_{\mathbf{k}+\mathbf{Q}} - E & U_{\mathbf{k}+\mathbf{Q}} & \Delta_{\mathbf{k}+\mathbf{Q}} \\ \Delta_{\mathbf{k}}^* & U_{\mathbf{k}+\mathbf{Q}}^* & -\varepsilon_{\mathbf{k}} - E & -G_{\mathbf{k}+\mathbf{Q}}^* \\ U_{\mathbf{k}}^* & \Delta_{\mathbf{k}+\mathbf{Q}}^* & -G_{\mathbf{k}}^* & -\varepsilon_{\mathbf{k}+\mathbf{Q}} - E \end{vmatrix} = 0. \quad (3)$$

The order parameter of the superconducting transition (ST) is given by the expression

$$\Delta_{\mathbf{k}_1} = \frac{1}{P_{pd}N} \sum_{\mathbf{k}} [2j(\mathbf{k}_1 - \mathbf{k}) - g(\mathbf{k}_1 - \mathbf{k}) + P_{pd}^2 B(\mathbf{k}_1, \mathbf{k}_1 - \mathbf{k})] \langle \Psi_{\mathbf{k}}^{\downarrow,2} \Psi_{-\mathbf{k}}^{\uparrow,2} \rangle, \quad (4)$$

where $j(\mathbf{q})$, $g(\mathbf{q})$, and $B(\mathbf{k}_1, \mathbf{q})$ are the Fourier transforms of the superexchange, Coulomb, and Fröhlich interactions potentials, respectively. Specifically,

$$j(\mathbf{q}) = j_0(1 - 6\delta^2) \cdot (\cos q_x a + \cos q_y a),$$

where $j_0 = 125$ meV for YBaCuO compounds¹⁰ and

$$g(\mathbf{q}) = g_0 \exp(-7\delta)(\cos q_x a + \cos q_y a),$$

where $g_0 = 315$ meV. Among all possible phonon modes, the buckling modes make the most important contribution to pairing. In this case

$$B(\mathbf{k}, \mathbf{q}) = 2B_0^2 \hbar \omega_{\mathbf{q}} \frac{1 + \frac{1}{2}[\cos q_x a + \cos q_y a]}{(\hbar \omega_{\mathbf{q}})^2 - (\varepsilon_{\mathbf{k}} - \varepsilon_{\mathbf{k}+\mathbf{q}})^2} \Theta(\hbar \omega_D - |\varepsilon_{\mathbf{k}} - \varepsilon_{\mathbf{k}+\mathbf{q}}|) \Theta(\hbar \omega_D - |\varepsilon_{\mathbf{k}}|), \quad (5)$$

$\hbar \omega_D$ is the Debye frequency of the order of 45 meV, $\Theta(x)$ is the theta function, and $B_0 \simeq 35$ meV. In the range of doping indices δ of interest to us, Eq. (4) has a solution of the form $\Delta_{\mathbf{k}} = \Delta_0(\cos k_x a - \cos k_y a)$.

As was pointed out in Ref. 5, the CDW parameter $G_{\mathbf{k}}$ is a sum of two components with a different dependence on the wave vector. The component associated with the short-range potentials

$$G_{\mathbf{k}_1}^{ex} = \frac{1}{P_{pd}N} \sum_{\mathbf{k}} [j(\mathbf{k}_1 - \mathbf{k}) + g(\mathbf{k}_1 - \mathbf{k})] \langle \Psi_{\mathbf{k}}^{2,\uparrow} \Psi_{\mathbf{k}+\mathbf{Q}}^{\uparrow,2} \rangle, \quad (6)$$

possesses d-type symmetry $G_{\mathbf{k}}^{ex} = iG_0(\cos k_x a - \cos k_y a)$, while the phonon part

$$G_{\mathbf{k}_1}^{ph} = \frac{P_{pd}}{N} \sum_{\mathbf{k}} V_{\mathbf{k},\mathbf{Q}} \langle \Psi_{\mathbf{k}+\mathbf{Q}}^{2\uparrow} \Psi_{\mathbf{k}}^{\uparrow 2} \rangle + V_{\mathbf{k}_1,\mathbf{Q}} \frac{P_{pd}}{N} \sum_{\mathbf{k}} \langle \Psi_{\mathbf{k}+\mathbf{Q}}^{2\uparrow} \Psi_{\mathbf{k}}^{\uparrow 2} \rangle, \quad (7)$$

possesses s-type symmetry. It is relatively small and is neglected below. The order parameter $U_{\mathbf{k}}$ entering in Eq. (3) is related with thermodynamic average $\langle \Psi_{\mathbf{k}}^{\downarrow 2} \Psi_{-\mathbf{k}-\mathbf{Q}}^{\uparrow 2} \rangle$, which appears naturally in the equations of motion in the presence of superconductivity and Peierls instability. In the general case it is determined by the expression

$$U_{\mathbf{k}_1} = \frac{1}{P_{pd}N} \sum_{\mathbf{k}} [j(\mathbf{k}_1 - \mathbf{k}) + j(\mathbf{k}_1 - \mathbf{k} - \mathbf{Q}) - g(\mathbf{k}_1 - \mathbf{k}) + P_{pd}^2 B(\mathbf{k}_1, \mathbf{k}_1 - \mathbf{k})] \langle \Psi_{\mathbf{k}}^{\downarrow 2} \Psi_{-\mathbf{k}-\mathbf{Q}}^{\uparrow 2} \rangle. \quad (8)$$

We investigate below the approximately optimal doping regime, where $Q \simeq (\pi, \pi)$. One can see from Eq. (8) that $U_{\mathbf{k}}$ is comparatively small and can possess only s symmetry, since for $Q = (\pi, \pi)$ the sum $j(\mathbf{k}_1 - \mathbf{k}) + j(\mathbf{k}_1 - \mathbf{k} - \mathbf{Q})$ vanishes. We note that for $U_{\mathbf{k}} = 0$ Eq. (3) leads to the spectrum

$$E_{1,2} = \sqrt{\frac{1}{2}(\varepsilon_{\mathbf{k}}^2 + \varepsilon_{\mathbf{k}+\mathbf{Q}}^2) + \Delta_{\mathbf{k}} \Delta_{\mathbf{k}}^* + G_{\mathbf{k}} G_{\mathbf{k}}^* \pm \frac{1}{2} E_{12}^2} \quad (9)$$

where

$$E_{12}^2 = \sqrt{(\varepsilon_{\mathbf{k}}^2 - \varepsilon_{\mathbf{k}+\mathbf{Q}}^2)^2 + 4G_{\mathbf{k}}G_{\mathbf{k}}^*(\varepsilon_{\mathbf{k}} + \varepsilon_{\mathbf{k}+\mathbf{Q}})^2 + 4\Delta_{\mathbf{k}}\Delta_{\mathbf{k}}^*(G_{\mathbf{k}} + G_{\mathbf{k}}^*)^2} \quad (10)$$

and $E_4 = -E_1$ and $E_3 = -E_2$.

In the general case we have the following system of integral equations:

$$\begin{aligned} \langle \Psi_{\mathbf{k}}^{\downarrow 2} \Psi_{-\mathbf{k}}^{\uparrow 2} \rangle &= \frac{P_{pd}\Delta_{\mathbf{k}}}{4} \left[\frac{1}{E_1} \tanh\left(\frac{E_1}{2k_B T}\right) + \frac{1}{E_1} \tanh\left(\frac{E_1}{2k_B T}\right) \right] \\ &\quad + \frac{P_{pd}N_{\Delta}}{2E_{12}^2} \left[\frac{1}{E_1} \tanh\left(\frac{E_1}{2k_B T}\right) - \frac{1}{E_1} \tanh\left(\frac{E_1}{2k_B T}\right) \right], \\ \langle \Psi_{\mathbf{k}}^{2\uparrow} \Psi_{\mathbf{k}+\mathbf{Q}}^{\uparrow 2} \rangle &= \frac{P_{pd}G_{\mathbf{k}}}{4} \left[\frac{1}{E_1} \tanh\left(\frac{E_1}{2k_B T}\right) + \frac{1}{E_1} \tanh\left(\frac{E_1}{2k_B T}\right) \right] \\ &\quad + \frac{P_{pd}N_G}{2E_{12}^2} \left[\frac{1}{E_1} \tanh\left(\frac{E_1}{2k_B T}\right) - \frac{1}{E_1} \tanh\left(\frac{E_1}{2k_B T}\right) \right], \\ \langle \Psi_{\mathbf{k}}^{\downarrow 2} \Psi_{-\mathbf{k}-\mathbf{Q}}^{\uparrow 2} \rangle &= \frac{P_{pd}U_{\mathbf{k}}}{4} \left[\frac{1}{E_1} \tanh\left(\frac{E_1}{2k_B T}\right) + \frac{1}{E_1} \tanh\left(\frac{E_1}{2k_B T}\right) \right] \\ &\quad + \frac{P_{pd}N_U}{2E_{12}^2} \left[\frac{1}{E_1} \tanh\left(\frac{E_1}{2k_B T}\right) - \frac{1}{E_1} \tanh\left(\frac{E_1}{2k_B T}\right) \right], \end{aligned} \quad (11)$$

where

$$\begin{aligned} N_{\Delta} &= \frac{1}{2}\Delta(\varepsilon_{\mathbf{k}}^2 - \varepsilon_{\mathbf{k}+\mathbf{Q}}^2) + \Delta_{\mathbf{k}}G_{\mathbf{k}}^*(G_{\mathbf{k}} + G_{\mathbf{k}}^*) + U_{\mathbf{k}}(\Delta_{\mathbf{k}}U_{\mathbf{k}}^* - \Delta_{\mathbf{k}}^*U_{\mathbf{k}}) + 2\varepsilon_{\mathbf{k}+\mathbf{Q}}G_{\mathbf{k}}^*U_{\mathbf{k}}, \\ N_G &= \frac{1}{2}G_{\mathbf{k}}(\varepsilon_{\mathbf{k}} + \varepsilon_{\mathbf{k}+\mathbf{Q}})^2 + \Delta_{\mathbf{k}}\Delta_{\mathbf{k}}^*(G_{\mathbf{k}} + G_{\mathbf{k}}^*) + \varepsilon_{\mathbf{k}+\mathbf{Q}}\Delta_{\mathbf{k}}^*U_{\mathbf{k}} - \varepsilon_{\mathbf{k}}\Delta_{\mathbf{k}}U_{\mathbf{k}}^*, \\ N_U &= \frac{1}{2}U_{\mathbf{k}}(\varepsilon_{\mathbf{k}} - \varepsilon_{\mathbf{k}+\mathbf{Q}})^2 - \Delta_{\mathbf{k}}(\Delta_{\mathbf{k}}U_{\mathbf{k}}^* - \Delta_{\mathbf{k}}^*U_{\mathbf{k}}) - \varepsilon_{\mathbf{k}}\Delta_{\mathbf{k}}G_{\mathbf{k}}^* + \varepsilon_{\mathbf{k}+\mathbf{Q}}\Delta_{\mathbf{k}}G_{\mathbf{k}}. \end{aligned} \quad (12)$$

The system of equations (11)-(13) was solved numerically. As expected, the parameter U_k is negligibly small. The computed phase diagram of the δ dependence of the critical temperatures for $\Delta_0(T_C)$ and $G_0(T^*)$ at $Q = (\frac{11}{12}\pi, \frac{11}{12}\pi)$ is close to the corresponding diagrams proposed in experimental works (see, for example, Ref. 11). In Fig. 1 three different doping cases are presented as an example of the temperature dependences found for the amplitudes of the order parameters $\Delta_0(T)$ and $G_0(T)$: α_1 , α_2 and α_3 , where the parameter α is given by the ratio $\alpha(\delta) = (\delta - \delta_{min})/(\delta_{opt} - \delta_{min})$. Here δ_{min} is the minimum value of the doping corresponding to the appearance of a superconducting state. In all cases, for $\delta < \delta_{opt} = 0.315$ (i.e., the existence of a CDW) the temperature dependence of the superconducting

order parameter differs considerably from the BCS case. In the case of a strongly overdoped regime the ratio $4\Delta_0/k_B T_C = 4.2$; for δ_{opt} it equals 4.5; it then increases, as seen in Fig. 1, and reaches values of the order of 10 for $\delta \gtrsim \delta_{min}$ (i.e., in the strongly underdoped region). This kind of variation of $4\Delta_0/k_B T_C$ has already been noted in a number of experimental works.¹² The computed temperature dependences of the pseudogap G_0 exhibit nonmonotonic behavior as temperature decreases; this has not been noticed previously. It would be interesting to check this prediction of the theory experimentally. Thus, if the effective gap parameter $\Delta_{eff}(T)$, determined as the energy interval between peaks in the density of states, is measured in scanning tunneling spectroscopy experiments (see, for example, Ref. 12), then on account of the nonmonotonic behavior of $G_0(T)$ anomalies should be observed in the plot for $\Delta_{eff}(T)$: 1) In type α_1 samples $\Delta_{eff}(T)$ will decrease (!) as $T \rightarrow 0$; 2) for $\alpha \approx \alpha_3$ a local minimum should be observed in the plot of $\Delta_{eff}(T)$. Examples of such plots calculated on the basis of expressions (9) and (10) are presented in Fig. 2. In our opinion the indicated anomalies can be seen from the experimental data.^{12,13} These results, however, require a more detailed experimental check on samples with different doping indices.

This work was supported in part by the Russian State Science and Technology Program "Superconductivity", Project No. 98014.

REFERENCES

- ¹ H. Ding, M. R. Norman, J. C. Campuzano et al., Phys. Rev. B 54, R9678 (1996).
- ² J. M. Harris, Z.-X. Shen, P. J. White et al., Phys. Rev. B 54, 15665 (1996); G. V. M. Williams, J. L. Tallon, E. M. Haines et al., Phys. Rev. Lett. 78, 721 (1997).
- ³ Yu. V. Kopaev, in The Problem of High-Temperature Superconductivity, edited by V. L. Ginzburg and D. A. Kirzhnits, Nauka, Moscow, 1978 (in Russian), (1982) (in English)
- ⁴ C. A. Balseiro and L. M. Falicov, Phys. Rev. B 20, 4457 (1979).
- ⁵ S. V. Varlamov, M. V. Eremin, and I. M. Eremin, JETP Lett. 66, 569 (1997).
- ⁶ M. V. Eremin, S. G. Solovyanov, and S. V. Varlamov, Zh. Eksp. Teor. Fiz. 112, 1763 (1997) JETP 85, 963 (1997).
- ⁷ Z.-X. Shen and D. S. Dessau, Phys. Rep. 253,1(1995).
- ⁸ I. Eremin, M. Eremin, S. Varlamov et al., Phys. Rev. B 56, 11305 (1997).
- ⁹ N. M. Plakida, R. Hayn, and J. L. Richard, Phys. Rev. B 51, 16599 (1995).
- ¹⁰ S. M. Hayden, G. Aeppli, T. G. Perring et al., Phys. Rev. B 54, R6905 (1996).
- ¹¹ G. V. M. Williams, J. L. Tallon, and J. W. Loram, Phys. Rev. B 58, 15053 (1998); G. V. M. Williams, J. L. Tallon, R. Michalak, and R. Dupree, Phys. Rev. B 54, R6909 (1996).
- ¹² Ch. Renner, B. Revaz, J.-Y. Genoud et al., Phys. Rev. Lett. 80, 149 (1998); N. Miyakawa, P. Guptasarma, J. Zasadzinski et al., Phys. Rev. Lett. 80, 157 (1998); Y. Sezaki, T. Ekino, and H. Fujii, in Abstracts of the Conference on Strongly Correlated Electron Systems, Paris, France, July 15-18, 1998; T. Ekino, Y. Sezaki, and H. Fujii, Phys. Rev. B, v. 60, pp. 6916-6922, (1999)
- ¹³ A. G. Loeser, Z.-X. Shen, M. C. Schabel et al., Phys. Rev. 56, 14185 (1997).

FIGURES

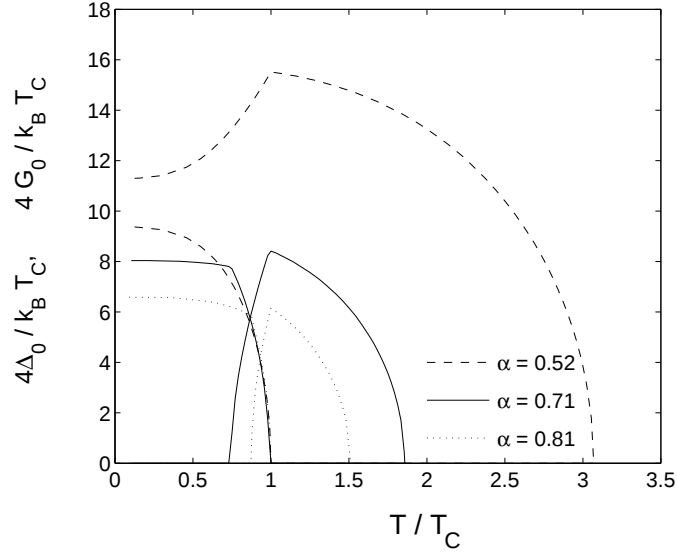


FIG. 1. Computed temperature dependences of the amplitudes of the order parameters Δ_0 and G_0 . The curves corresponding to the superconducting gap parameter Δ_0 start at the point $T/T_C = 1$. The relative-doping parameter α is defined in the text.

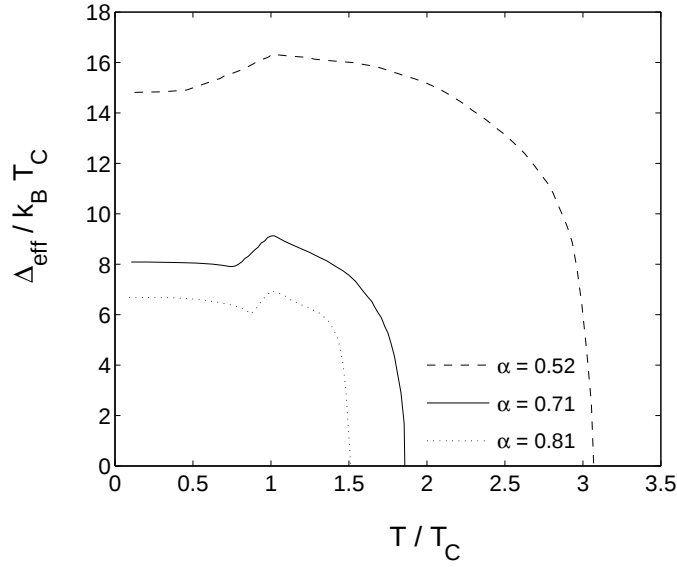


FIG. 2. Predicted examples of nonmonotonic temperature variations of the effective gap Δ_{eff} between peaks of the density of states of the energy spectrum.